

इंटरनेट

मानक

Disclosure to Promote the Right To Information

Whereas the Parliament of India has set out to provide a practical regime of right to information for citizens to secure access to information under the control of public authorities, in order to promote transparency and accountability in the working of every public authority, and whereas the attached publication of the Bureau of Indian Standards is of particular interest to the public, particularly disadvantaged communities and those engaged in the pursuit of education and knowledge, the attached public safety standard is made available to promote the timely dissemination of this information in an accurate manner to the public.

“जानने का अधिकार, जीने का अधिकार”

Mazdoor Kisan Shakti Sangathan


“The Right to Information, The Right to Live”

“पुराने को छोड़ नये के तरफ”

Jawaharlal Nehru

“Step Out From the Old to the New”

IS 9295 (1983): Steel tubes for idlers for belt conveyors
[MTD 19: Steel Tubes, Pipes and Fittings]

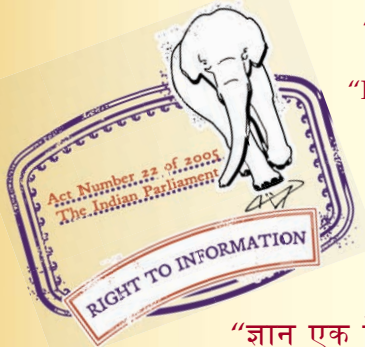

“ज्ञान से एक नये भारत का निर्माण”

Satyanarayan Gangaram Pitroda

“Invent a New India Using Knowledge”



“ज्ञान एक ऐसा खजाना है जो कभी चुराया नहीं जा सकता है”

Bhartrhari—Nitiśatakam

“Knowledge is such a treasure which cannot be stolen”

IS : 9295 - 1983
(Reaffirmed 1995)

Indian Standard
SPECIFICATION FOR
STEEL TUBES FOR IDLERS FOR
BELT CONVEYORS
(*First Revision*)

Third Reprint JULY 1997
(Incorporating Amendment No. 1)

UDC 621.643,2 [669.14] : 621.867.218.051.44

© Copyright 1997

BUREAU OF INDIAN STANDARDS
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI 110002

Gr 3

May 1983

IS : 9295 - 1983
(Reaffirmed 1995)

Indian Standard
SPECIFICATION FOR
STEEL TUBES FOR IDLERS FOR
BELT CONVEYORS
(*First Revision*)

Steel Tubes, Pipes and Fittings Sectional Committee, SMDC 22

<i>Chairman</i>	<i>Representing</i>
SHRI S. C. DHINGRA	Ministry of Industry
<i>Members</i>	
SHRI A. S. AGARWAL	Steel Tubes of India Ltd, Dewas
SHRI R. S. PATHAK (<i>Alternate</i>)	
SHRI K. N. AHUJA	Federation of Engineering Industries of India, New Delhi
SHRI A. S. SHARMA (<i>Alternate</i>)	
SHRI S. C. ANAND	Bharat Steel Tubes Ltd, New Delhi
SHRI R. K. ABROL (<i>Alternate</i>)	
SHRI S. N. BASU	Directorate General of Supplies and Disposals (Inspection Wing), New Delhi
SHRI T. N. UROVEJA (<i>Alternate</i>)	
SHRI H. S. BEDI	Steel Authority of India Ltd (Rourkela Steel Plant)
SHRI P. K. MOHAPATRA (<i>Alternate</i>)	
SHRI D. P. BHATTACHARJEE	Export Inspection Council, Calcutta
SHRI S. C. ARORA (<i>Alternate</i>)	
SHRI B. B. CHAKRAVERTI	Suprintendence Co of India (P) Ltd, Calcutta
SHRI A. K. SHOME (<i>Alternate</i>)	
SHRI L. M. CHAUDHRI	Public Works Department (Public Health Branch), Chandigarh
SHRI K. K. GANDHI (<i>Alternate</i>)	
DEPUTY DIRECTOR STANDARDS (LOCO)	Research, Designs and Standards Organization (Ministry of Railways), Lucknow
CHEMIST AND METALLURGIST-I (RDSO) (<i>Alternate</i>)	
LT-CDR GURDARSHAN SINGH	Engineer-in-Chief's Branch, Army Headquarters, New Delhi
SHRI RAJENDAR SINGH (<i>Alternate</i>)	
SHRI SUSHIL JAIN	Jain Tube Co Ltd, Ghaziabad
SHRI M. M. LAL (<i>Alternate</i>)	

(*Continued on page 2*)

© Copyright 1983

BUREAU OF INDIAN STANDARDS

This publication is protected under the *Indian Copyright Act* (XIV of 1957) and reproduction in whole or in part by any means except with written permission of the publisher shall be deemed to be an infringement of copyright under the said Act.

IS : 9295 - 1983

(Continued from page 1)

<i>Members</i>	<i>Representing</i>
SRI S. C. JAIN	Jindal Pipes Ltd, Ghaziabad
SRI A. S. SHARMA (Alternate)	
SRI JASWANT SINGH	Directorate General of Technical Development, New Delhi
SRI S. C. NAOPAL (Alternate)	
SRI ONKAR S. KANWAR	Association of Indian Engineering Industry, New Delhi
SRI P. R. GUPTA (Alternate)	
SRI H. M. KAUL	Ministry of Agriculture
SRI M. C. KESAVA RAO	Hindustan Shipyard Ltd, Vishakhapatnam
SRI P. L. NARASIMHAM (Alternate)	
SRI B. KUMAR	Stewarts and Lloyds of India Ltd, Calcutta
SRI T. K. BASU (Alternate)	
SRI S. KUMAR	Indian Register of Shipping, Bombay
SRI S. CHANDRA (Alternate)	
SRI M. C. KUMARASWAMY	Indian Tube Co Ltd, Jamshedpur
SRI D. DUTTA (Alternate)	
SRI K. MUKHERJEE	The Fertilizer (Planning and Development) India Ltd, Sindri
SRI R. K. SINHA (Alternate)	
SRI S. NEELAKANTAN	Zenith Steel Pipes & Industries Ltd, Khopoli
DR A. R. KESKAR (Alternate)	
SRI V. RATNAM VELICHETTY	Bharat Heavy Electricals Ltd, Tiruchchirappalli
SRI G. P. SARABHAI	Oil and Natural Gas Commission, Dehra Dun
SRI V. K. CHATURVEDI (Alternate)	
SRI APOORVA SHAH	Gujarat Steel Tubes Ltd, Ahmadabad
SRI H. J. THAKER (Alternate)	
SRI P. T. SHANKARAN NAYAR	Central Boilers Board, New Delhi
SRI G. S. GOSAL (Alternate)	
SRI E. SUBBA RAO	Indian Oil Corporation Ltd, Bombay
SRI P. C. JOHARI (Alternate)	
SRI B. R. TANEJA	The Indian Seamless Metal Tubes Ltd, Bombay
SRI O. P. KAKKAR (Alternate)	
SRI C. R. RAMA RAO, Director (Struc & Met) (Secretary)	Director General, ISI (<i>Ex-officio Member</i>)

**Panel for Drafting Specification for Steel Pipes for Idlers for
Troughed Belt Conveyors, SMDC 22 : P26**

<i>Convener</i>	
SRI H. J. THAKER	Gujarat Steel Tubes Ltd, Ahmadabad
<i>Members</i>	
SRI R. K. ABROL	Bharat Steel Tubes Ltd, New Delhi
SRI S. C. ANAND (Alternate)	
SRI S. D. S. BHALLA	Kalinga Tubes Ltd, Cuttack
SRI N. C. MOHANTY (Alternate)	

(Continued on page 11)

AMENDMENT NO. 2 NOVEMBER 2006
TO
IS 13428 : 2005 PACKAGED NATURAL MINERAL
WATER — SPECIFICATION

(Second Revision)

[Page 4, clause 8.1(a)] --- Substitute the following for the existing:

'a) Name of the product (that is natural mineral water);'

(FAD 14)

AMENDMENT NO. 3 JUNE 2010
TO
IS 9295 : 1983 SPECIFICATION FOR STEEL TUBES FOR
IDLERS FOR BELT CONVEYORS

(First Revision)

(Page , clause 18.1) — Substitute ‘embossed’ for ‘marked’.

(MTD 19)

Reprography Unit, BIS, New Delhi, India

Indian Standard
SPECIFICATION FOR
STEEL TUBES FOR IDLERS FOR
BELT CONVEYORS
(*First Revision*)

0. FOREWORD

0.1 This Indian Standard (First Revision) was adopted by the Indian Standards Institution on 18 April 1983, after the draft finalized by the Steel Tubes, Pipes and Fittings Sectional Committee had been approved by the Structural and Metals Division Council.

0.2 Steel tubes are extensively used as idlers for belt conveyors and the standard covering requirements for the same was first published in 1979. While reviewing the standard, it was felt necessary to issue a revision incorporating the following salient changes in the light of the experience gained in usage of the standard by the industry and the users.

- a) Amendment No. 1, issued in September 1981.
- b) Certain additional thicknesses and modifications to the requirements given earlier for ovality, eccentricity, straightness, tolerances on thickness, fin height, etc.

0.3 For the purpose of deciding whether a particular requirement of this standard is complied with, the final value, observed or calculated, expressing the result of a test or analysis, shall be rounded off in accordance with IS : 2-1960*. The number of significant places retained in the rounded off value should be the same as that of the specified value in this standard.

1. SCOPE

1.1 This standard covers the requirements for steel tubes for idlers for belt conveyors.

*Rules for rounding off numerical values (*revised*).

IS : 9295 - 1983

2. TYPES AND GRADES

2.1 Steel tubes for idlers for belt conveyors shall be of the following types (based on the process of manufacture and grades):

<i>Types</i>	<i>Grades</i>
Hot-Finish Seamless (HFS)	YSt 210, YSt 240 and YSt 310
Cold-Drawn Seamless (CDS)	YSt 210, YSt 240 and YSt 310
ERW (including HFIW)	YSt 210, YSt 240 and YSt 310

NOTE — The grades YSt 210, YSt 240 and YSt 310 correspond to grades 22, 25 and 32 specified in the original standard.

3. SUPPLY OF MATERIAL

3.1 General requirements relating to the supply of steel tubes for idlers for belt conveyors shall conform to IS : 1387-1967*.

4. DESIGNATION

4.1 Steel tubes are designated by the symbols to indicate the process of manufacture, followed by the minimum yield stress in MPa.

5. MATERIAL

5.1 The tube shall be made from the steel manufactured by open hearth basic oxygen, electric furnace, or any other process approved by the purchaser, or a combination of these processes.

6. MANUFACTURE

6.1 Tubes shall be manufactured by one of the following processes:

- a) Seamless, and
- b) ERW (including HFIW).

6.2 The height of the internal fin value of ERW pipes shall not exceed 1.7 mm.

NOTE — Lower limit of fin height may be as agreed to between the manufacturer and the purchaser.

7. CHEMICAL COMPOSITION

7.1 The ladle analysis of steel shall not have more than 0.06 percent sulphur and not more than 0.06 percent phosphorus and shall be carried

*General requirements for the supply of metallurgical materials (first revision).

out either by the method specified in IS : 228* and its relevant parts or any other established instrumental/chemical method. In case of dispute the procedure given in relevant part of IS : 228* shall be the referee method. However, where the method is not given in IS : 228* and its relevant parts, the referee method shall be agreed to between the purchaser and the manufacturer.

7.2 Check Analysis — When specified on the purchase order, a check analysis shall be made by the supplier. The permissible variation from the limits specified in 7.1 shall be as follows:

<i>Constituents</i>	<i>Percent, Max</i>
Phosphorus	0.005
Sulphur	0.005

8. MECHANICAL PROPERTIES

8.0 The following tests shall be carried out.

8.1 Tensile Test — This test shall be carried out in accordance with IS : 1894-1972† on one of the following, at the manufacturer's option:

- A length cut from the end of the selected tube (the ends being plugged for grips or flattened where necessary), and
- A longitudinal strip cut from the tube and tested in the curved condition.

8.1.1 The tensile strength, the yield stress and the percentage elongation shall be not less than those specified in Table 1.

TABLE 1 MECHANICAL PROPERTIES

TUBE DESIGNATION	TENSILE STRENGTH	YIELD STRESS	ELONGATION
	MPa <i>Min</i>	MPa <i>Min</i>	PERCENT <i>Min</i>
HFS 210/CDS 210/ERW 210	330	210	20
HFS 240/CDS 240/ERW 240	410	240	18
HFS 310/CDS 310/ERW 310	450	310	15

8.1.2 The percentage elongation in this standard shall be reported with reference to a gauge length of $5.65 \sqrt{S_0}$ where S_0 is the original cross sectional area of the test specimen.

*Methods of chemical analysis of steels (issued in parts).

†Methods for tensile testing of steel tubes (first revision).

IS : 9295 - 1983

8.2 Drift Expansion Test — The test shall be carried out on a piece of tube approximately 100 mm long, cut from end of each selected tube in accordance with IS : 2335-1963* and the minimum increase in outside diameter after expansion shall be 2.5 percent. The included angle shall be 30°, 45°, or 60°, at the option of the manufacturer.

NOTE — The sizes which are not covered in IS : 2335-1963* shall be subject to agreement between the purchaser and the manufacturer.

8.3 Flattening Test — A ring not less than 50 mm in length, cut from one end of each selected tube shall be flattened between the two parallel plates in accordance with IS : 2328-1963† with weld at 45°, if any. No opening shall occur by flattening in the weld, until the distance between the plates is less than 75 percent of the original outside diameter of the pipe. No cracks or breaks in the material shall occur until the distance between the plates is less than 60 percent of the original outside diameter.

9. WEIGHT

9.1 The nominal mass and dimensions of black steel tubes shall be as specified in Table 2.

TABLE 2 DIMENSIONS AND NOMINAL MASSES OF BLACK STEEL TUBES

OUTSIDE DIAMETER (1) mm	THICKNESS (2) mm	MASS (3) kg/m
63.5	3.65, 4.50	5.39, 6.55
76.1	3.65, 4.50	6.52, 7.95
88.9	4.05, 4.85, 6.30	8.47, 10.05, 12.83
101.6	4.05, 4.85, 6.30	9.74, 11.57, 14.81
108.0	4.05, 4.85, 6.30	10.38, 12.34, 15.8
114.3	4.5, 5.4, 6.3	12.19, 14.50, 16.78
120.0	4.5, 5.4, 6.3	12.82, 15.26, 17.67
127.0	4.5, 4.85, 5.4, 6.3	13.6, 14.61, 16.19, 18.75
133.0	4.5, 4.85, 5.4, 6.3	14.3, 15.33, 16.99, 19.69
139.7	4.5, 4.85, 5.4, 6.3	15.0, 16.13, 17.89, 20.73
152.4	4.5, 4.85, 5.4, 6.3	16.4, 17.65, 19.58, 22.70
159.0	4.5, 4.85, 5.4, 6.3	17.1, 18.44, 20.46, 23.72
165.1	4.5, 4.85, 5.4, 6.3	17.8, 19.17, 21.27, 24.67
168.3	4.5, 4.85, 5.4, 6.3	18.2, 19.55, 21.69, 25.17
193.7	5.4, 6.3, 7.1	25.1, 29.12, 32.67
219.1	5.4, 6.3, 7.1	28.5, 33.06, 37.12

*Method for drift expanding test on steel tubes.

†Method for flattening test on steel tubes.

9.1.1 Outside diameters and thicknesses other than those covered under the standard will be permissible subject to agreement between the manufacturer and the purchaser.

10. HARDNESS TEST

10.1 When hardness values are required, the hardness values shall be as agreed to between the purchaser and the manufacturer.

11. NUMBER OF SAMPLES FOR MECHANICAL TESTS AND DIMENSIONS

11.1 **Mechanical Tests** — The number of pipes on which mechanical tests shall be performed are as follows:

- a) *Up to and including 114.30 mm outside diameter* — One tube from a lot of 400 tubes or a fraction thereof as presented for inspection, and
- b) *Over 114.30 mm outside diameter* — One pipe from a lot of 200 pipes or a fraction thereof as presented for inspection.

11.2 **Dimensions** — One tube from a lot of 100 tubes or fraction thereof as presented for inspection.

12. RETESTS

12.1 Should any one of the test pieces first selected fail to pass any of the tests specified, two further samples shall be selected for testing in respect of each failure from the same lot. Should the test pieces from both these additional samples pass, the material represented by the test samples shall be deemed to comply with the requirement of that particular test. Should the test pieces from either of these additional samples fail, the material represented by the test samples shall be deemed as not complying with the standard or the manufacturer may select to test individually the remaining lengths in the lot for the test failed to comply in the preceding tests.

13. TOLERANCES

13.1 Tubes shall conform to the following tolerances.

13.1.1 *Ovality* — It is defined as $OD, Max - OD, Min$ and at any one cross section shall not exceed:

Below 168.3 mm	0.5 mm
Including 168.3 mm and above	1.0 mm

IS : 9295 - 1983

13.1.2 Eccentricity — Eccentricity at any cross section, when calculated by the following formula shall not exceed 5 percent:

$$\frac{t_{\max} - t_{\min}}{2 \times t} \times 100$$

where

- t_{\max} = maximum thickness,
- t_{\min} = minimum thickness, and
- t = specified thickness.

13.1.3 Mass

- a) Single tube (medium and heavy series) shall have a tolerance of ± 10 percent, and
- b) For quantities per load of 10 tonnes, *Min* the tolerance shall be ± 7.5 percent (medium and heavy series).

NOTE — For the purpose of a minimum weighment of 10 tonnes lot, the weighment may be done in convenient lots at the option of the manufacturer.

13.1.4 The tolerances of HFS/ERW tubes shall be as under:

HFS/ERW	Tolerances
a) Outside diameter	± 0.8 percent
b) Thickness	± 10 percent

13.1.5 The tolerances on CDS tubes shall be as under.

13.1.5.1 Outside diameter — Where the ratio of outside diameter to thickness is not greater than 33:1, the tolerances shall be as shown in Table 3.

13.1.5.2 For sizes larger than 127.0 mm outside diameter, the tolerance shall be $\pm (0.08 \text{ mm} + 0.05 \text{ per } 25 \text{ mm of outside diameter or part thereof})$.

13.1.5.3 Where ratio of outside diameter to thickness is greater than 33:1 the tolerances shall be as agreed to between the purchaser and the manufacturer.

13.1.5.4 Thickness — The tolerance on thickness shall be ± 10 percent.

14. WORKMANSHIP

14.1 All tubes shall be free from harmful defects, reasonably smooth and free from rust. Unless otherwise specified, ends shall be cut square. Surface finish shall be as agreed to between the manufacturer and the purchaser.

TABLE 3 TOLERANCES

All dimensions in millimetres.

OUTSIDE DIAMETER		TOLERANCE
Over	Up to and Including	(3)
(1)	(2)	
—	25.4	±0.13
25.4	38.1	±0.15
38.1	51.0	±0.18
51.0	63.5	±0.20
63.5	76.1	±0.23
76.1	88.9	±0.25
88.9	101.6	±0.28
101.6	114.3	±0.31
114.3	127.0	±0.33

15. STRAIGHTNESS*

15.1 Unless other tolerances are agreed to between the purchaser and the manufacturer, tubes shall not deviate from straightness by more than 1/1 000 of any length, when measured at the centre of that length, at the manufacturer's works.

16. LENGTH

16.1 The tubes shall be supplied in random lengths of 4 to 7 metres unless otherwise agreed to between the manufacturer and the purchaser.

16.2 Where 'exact' or 'cut length' is specified, it shall be within the tolerance of $\pm \frac{6}{0}$ mm.

17. SURFACE PROTECTION

17.1 Unless otherwise specified, the tubes shall be supplied with protective coating by rust preventive oil on the outside surface.

18. MARKING

18.1 Each tube may be marked with the manufacturer's name or trade-mark.

18.2 Each bundle of tubes shall be marked suitably with the following:

- a) Type of pipe,
- b) Grade of material, and
- c) Outside diameter and thickness.

IS : 9295 - 1983

18.2.1 Each tube may also be marked with the ISI Certification Mark.

NOTE — The use of the ISI Certification Mark is governed by the provisions of the Indian Standards Institution (Certification Marks) Act and the Rules and Regulations made thereunder. The ISI Mark on products covered by an Indian Standard conveys the assurance that they have been produced to comply with the requirements of that standard under a well-defined system of inspection, testing and quality control which is devised and supervised by ISI and operated by the producer. ISI marked products are also continuously checked by ISI for conformity to that standard as a further safeguard. Details of conditions, under which a licence for the use of the ISI Certification Mark may be granted to manufacturers or processors, may be obtained from the Indian Standards Institution.

(Continued from page 2)

<i>Members</i>	<i>Representing</i>
SHRI M. K. V. CHARI	McNally Bharat Engineering Co Ltd, Kumardhubi
SHRI S. K. CHAUDHURI (Alternate)	
SHRI H. N. FUTEHALLY	Dynacraft Machine Co Ltd, Bombay
SHRI S. K. DRAGO (Alternate)	
SHRI O. S. KANWAR	Association of Indian Engineering Industry, New Delhi
SHRI P. R. GUPTA (Alternate)	
SHRI T. S. KASTURI	Neyveli Lignite Corporation Ltd, Neyveli
SHRI M. C. RENGARAJAN (Alternate)	
SHRI C. S. ROY	Mining & Allied Machinery Corporation Ltd, Durgapur
SHRI S. K. MUKHERJI (Alternate)	
SHRI R. N. SAH	Tata Robins Frazer Ltd, Jamshedpur
SHRI V. P. NIJHAWAN (Alternate)	
SHRI V. C. SHARMA	Indian Tube Co Ltd, Jamshedpur
SHRI S. SUR	Elecon Engineering Co Ltd, Vidyanagar
SHRI H. S. NORONHA (Alternate)	

BUREAU OF INDIAN STANDARDS

Headquarters

Manak Bhavan, 9 Bahadur Shah Zafar Marg NEW DELHI 110002
Telephones 323 0131, 323 3375, 323 9402
Fax 91 11 3234062, 91 11 3239399 91 11 3239382

Telegrams Manaksanstha
(Common to all Offices)
Telephone

Central Laboratory

Plot No 20/9, Site IV, Sahibabad Industrial Area, Sahibabad 201010 8-77 00 32

Regional Offices:

Central Manak Bhavan, 9 Bahadur Shah Zafar Marg NEW DELHI 110002 323 76 17
*Eastern 1/14 CIT Scheme VII M, V I P Road Maniktola, CALCUTTA 700054 337 86 62
Northern SCO 335-336, Sector 34-A, CHANDIGARH 160022 60 38 43
Southern C I T Campus, IV Cross Road, CHENNAI 600113 235 23 15
†Western Manakalaya, E9, Behind Marol Telephone Exchange, Andheri (East),
MUMBAI 400093 832 92 95

Branch Offices:

'Pushpak', Nurmohamed Shaikh Marg, Khanpur, AHMEDABAD 380001 550 13 48
‡Peenya Industrial Area, 1st Stage, Bangalore Tumkur Road,
BANGALORE 560058 839 49 55
Gangotri Complex, 5th Floor, Bhadbhada Road T T Nagar, BHOPAL 462003 55 40 21
Plot No 62-63, Unit VI, Ganga Nagar, BHUBANESHWAR 751001 40 36 27
Kalaikathir Buildings, 670 Avinashi Road, COIMBATORE 641037 21 01 41
Plot No 43, Sector 16 A, Mathura Road, FARIDABAD 121001 8 28 88 01
Savitri Complex, 116 G T Road, GHAZIABAD 201001 8-71 19 96
53/5 Ward No 29, R G Barua Road, 5th By-lane, GUWAHATI 781003 54 11 37
5-8-56C, L N Gupta Marg, Nampally Station Road, HYDERABAD 500001 20 10 83
E-52, Chitaranjan Marg, C-Scheme, JAIPUR 302001 37 29 25
117/418 B, Sarvodaya Nagar, KANPUR 208005 21 68 76
Seth Bhawan, 2nd Floor, Behind Leela Cinema, Naval Kishore Road,
LUCKNOW 226001 23 89 23
NIT Building, Second Floor, Gokulpat Market, NAGPUR 440010 52 51 71
Patliputra Industrial Estate, PATNA 800013 26 23 05
Institution of Engineers (India) Building 1332 Shivaji Nagar, PUNE 411005 32 36 35
T C No 14/1421, University P O Palayam, THIRUVANANTHAPURAM 695034 6 21 17

*Sales Office is at 5 Chowringhee Approach, P O Princep Street,
CALCUTTA 700072 27 10 85
†Sales Office is at Novelty Chambers, Grant Road, MUMBAI 400007 309 65 28
‡Sales Office is at 'F' Block, Unity Building, Narashimaraja Square,
BANGALORE 560002 222 39 71